
Type 11 Category: Wall elements


Cast-in-place interior walls

Location

Ground-floor

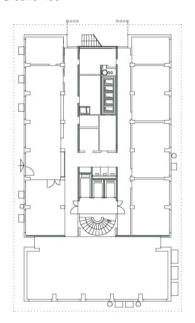

All other floors

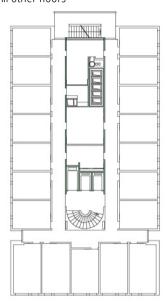

Cast-in-place interior wall

Ground-floor



Type 11	Category :	Wall elements
Cast-in-place interior walls		

Description			Condition and durability			
Exposition	Inside, not exposed		Condition assessment	100% good		
Color	Shade of grey or white painted					
Finishing	Horizontal wood plank patterns or crepis		Carbonatation depth [mm]	Avg. 8 (max 20)		
Actual location	All floors		Toxic substance	None		
Initial function	Wall load-bearing element					
Accessibility	Difficult – three & more elements to dismantle before		Mechanical characteristics			
Anchor points	Not available			Density	2500 kg/m³	
Overlays	Туре	Fixation	Thickness	Concrete compressive strength	69 N/mm ²	
From concrete	Mortar	-	10 mm	Concrete young modulus	41′500 N/mm ²	
To surface	Wallpaper	Glued	-	Reinforcement tensile strength	450 N/mm ²	
Connexion type	Connected to c	ast-in-place slab	S	Reinforcement young modulus	205'000 N/mm ²	
Deconstruction tool	Diamond saw o	or hydro-blasting				

Element	Geometry			Inventory				Environmental impacts	
Subtype	Dimensions (LxHxT) [mm]	Reinforcement [mm]	Cross-section resistance [kNm/m]	Quantity [m²]	Weight [kg/ m²]	Total volume [m³]	Significance	Initial production [kgCO2-eq/ m²]	Conventional demolition [kgCO2-eq/ m²]
1st to 14th floor	L x 2460 x 150	Ø 8 S = 250	9,5	(1560)	375	234	3,4%	(33)	4
Ground floor	L x 2540 x 150	Ø 8 S = 250	9,5	360	375	54	0,8%	33	4

Additional information

Additional note	>	The only core tested for the cast-in-place interior walls showed an abnormally low result. The strength of the
		concrete was estimated to be equal to the one of the cast-in-place facade walls since they were probably
		cast at the same time.
Attention point	-	

